



## Hydroxyapatite Prepared by Co-Precipitation with Calcium Carbonate:

### Effects of Digested Calcium Carbonate and Phosphate Sources

Wallika Suksomran<sup>a\*</sup> and Robert Molloy<sup>b</sup>

<sup>a</sup> Faculty of Science and Technology, Thepsatri Rajabhat University, Mueang, Lopburi, Thailand, 15000

<sup>b</sup> Polymer Research Laboratory, Department of Chemistry, Faculty of Science, Chiang Mai University, Chiang Mai, Thailand, 50200

\* Corresponding author. E-mail address: wallika.s@gmail.com

Received: 12 May 2016; Accepted: 10 August 2016

#### Abstract

The Hydroxyapatite (HAP) was prepared by co-precipitation of calcium carbonate ( $\text{CaCO}_3$ ) with various orthophosphate sources such as phosphoric acid ( $\text{H}_3\text{PO}_4$ ), ammonium dihydrogen phosphate ( $\text{NH}_4\text{H}_2\text{PO}_4$ ) and diammonium hydrogen phosphate ( $(\text{NH}_4)_2\text{HPO}_4$ ) under ambient conditions.  $\text{CaCO}_3$  was digested by 20%  $\text{HNO}_3$  to produce calcium cation which reacted with the orthophosphate ion to form hydroxyapatite. All XRD patterns closely matched with the HAP reference data. There was no change in the sharpness of the diffraction peaks and little or no change in the peak intensity was observed when compared to various phosphate sources ( $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$  and  $(\text{NH}_4)_2\text{HPO}_4$ ). The FTIR spectrum showed without the characteristic bands of B-type  $\text{CO}_3^{2-}$  substitution at  $1421\text{--}1473\text{ cm}^{-1}$  ( $\nu_3$ ) and  $874\text{ cm}^{-1}$  ( $\nu_2$ ). Moreover, the FTIR spectrum showed without the characteristic peak of A-type  $\text{CO}_3^{2-}$  substitution at  $1540\text{ cm}^{-1}$ . The precipitation of HAP from digested  $\text{CaCO}_3$  solution occurred at 3 hours, while the reaction from non-digested  $\text{CaCO}_3$  solution occurred at 18 hours. The digestion of  $\text{CaCO}_3$  reduced the preparation time of HAP and also decreased the  $\text{CO}_3^{2-}$  substitution in HAP.

**Keywords:** Hydroxyapatite, Calcium carbonate, Co-precipitation

#### Introduction

Hydroxyapatite (HAP), whose chemical formula is  $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$ , is one of the most biocompatible materials due to its similarity with mineral constituents found in hard tissues such as teeth and bones. It is a very attractive material for biomedical applications, such as a bone substitute material in orthopedics and dentistry due to its excellent biocompatibility, bioactivity, and osteoconduction properties. In addition, HAP has a wider scope of applications in diverse fields like chromatography, solid state ionics, catalysts, drug delivery systems and fuel cells. It has a promising application as a chemical gas sensor (Mahabole, Aiyer, Ramakrishna, Sreedhar, & Khairnar, 2005). Various processes have been employed to prepare HAP powders, including chemical co-precipitation

(Inthong, Tunkasiri, Eitssayeam, Pengpat, & Rujijanagul, 2013), the sol-gel process, ultrasonication technique, microwave assisted technique (Waheeda, Sultana, Jamila, & Hussainb, 2013), ultrasonic spray-pyrolysis (An et al., 2007), hydrothermal syntheses (Kim & Ohtsuki, 2016), emulsion processing (Sonoda, Furuzono, Walsh, Sato, & Tanaka, 2002) and mechanochemical method (Nasiri-Tabrizi, Honarmandi, Ebrahimi-Kahrizsangi, & Honarmandi, 2009). Among these processes, chemical co-precipitation is the most promising method because of its simplicity in experimental operations, low operating temperature, and high yields of pure products (Kong, Ma, & Boey, 2002). For example, Bouyer, Gitzhofer, and Boulos. (2000) prepared nanometer size HAP crystals through a wet chemical precipitation method at different synthesis temperatures and with various



reactant addition rates. This work shows that shape, size, and specific surface area of the HAP nanoparticles are very sensitive to the reaction temperature and also to the reactant addition rate. The measured pH at the end of synthesis, which is strongly linked with the reactant addition rate, is a key parameter which can be used to determine the purity of the synthesized HAP nanocrystals and also for the stabilization (dispersion) of the suspension. Bezzi et al. (2003) prepared HAP by a sol-gel method, using  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  and  $(\text{NH}_4)_2\text{HPO}_4$  as raw materials, and EDTA and urea as aids. The above studies showed a trend to superfine in the development of HAP suspension polymerization dispersants. Kong et al. (2002) prepared nanosized hydroxyapatite powders by a co-precipitation process which used calcium nitrate and phosphoric acid as starting materials. The average grain size of the HAP powders were found to be 50–70 nm and showed no change when calcined at temperatures up to 600°C for 4 hours. Dense HAP ceramics were also obtained by sintering the synthesized HAP powders at temperatures from 1000°C to 1200°C with a final average grain size of 2 to 7  $\mu\text{m}$  correspondingly. Piantone, Bodénan, Derie, and Depelsenaire. (2003) examined the reaction of phosphate with various mineral species and described the usual sequence of events when calcium ions react in solution with phosphate: the first mineral species to precipitate was  $\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$  (brushite), followed by  $\text{Ca}_3(\text{PO}_4)_2$  (whitlockite),  $\text{Ca}_4\text{H}(\text{PO}_4)_3 \cdot 5\text{H}_2\text{O}$  (octacalcium phosphate), and, finally,  $\text{Ca}_5(\text{PO}_4)_3\text{OH}$  (hydroxylapatite). The theoretical phase diagram describing the stable minerals in pH vs. total  $\text{CO}_3^{2-}$  coordinates showed that when the  $\text{CO}_2$  gas partial pressure was near atmospheric pressure there was a narrow pH range between 6 and 9.5 where calcite could be converted into apatite. Verwilghen et al. (2009) synthesized HAP starting from  $\text{CaCO}_3$  and

monoammoniumphosphate in stoichiometric amounts. The novel aspect concerned the reaction conditions, which were simply mixing the reactants in water at ambient pressure and a temperature of 60°C. The reaction was continued for 72 hours. The  $\text{CaCO}_3$  solid phase slowly produced  $\text{CO}_2$  gas and buffered the solution at a pH value of 8.5 where HAP precipitated. Besides, the synthesis of calcium HAP starting from  $\text{CaCO}_3$  and different orthophosphate sources, including orthophosphoric acid, potassium, sodium, and ammonium dihydrogen orthophosphates was investigated under ambient conditions. The reaction started with  $\text{CaCO}_3$  dissolution in an acid medium, followed by rapid precipitation of calcium cations with orthophosphate species to form calcium phosphate. The reaction was continued for 48 hours under ambient conditions (25°C, atmospheric pressure). Orthophosphoric acid was the most interesting orthophosphate source since it was the most efficient for the dissolution of  $\text{CaCO}_3$  and was the only reactant leading to complete consumption by precipitation of the starting orthophosphate species within 48 hours (Minh, Lyczko, Sebei, Nzihou, & Sharrock, 2012). However, investigation focusing on the acid digestion of  $\text{CaCO}_3$  before HAP formation has not yet to be published. In this study, the  $\text{CaCO}_3$  was first digested with acid to form as  $\text{Ca}^{2+}$  ions. The digested  $\text{CaCO}_3$  was used to prepare HAP powder with various orthophosphate sources. The synthesized HAP powders were characterized by XRD, SEM, and FTIR measurement. The HAP powder was also prepared from non-digested  $\text{CaCO}_3$  by the same method for comparison.

## Materials and Methods

### Synthesis and characterization of hydroxyapatite





A fine powder of calcium carbonate ( $\text{CaCO}_3$ , 99%, Carlo Erba) was used as calcium source. Orthophosphoric acid ( $\text{H}_3\text{PO}_4$ , 85%, Ajax Finechem), ammonium dihydrogen orthophosphate ( $\text{NH}_4\text{H}_2\text{PO}_4$ , 98%, Ajax Finechem), and diammonium hydrogen orthophosphate ( $(\text{NH}_4)_2\text{HPO}_4$ , 98%, Ajax Finechem) were used as orthophosphate sources without further modification.  $\text{CaCO}_3$  (10 g) was digested by 40 mL of the 20% (w/v)  $\text{HNO}_3$  (69.5%, Carlo Erba). The solution mixture was topped up with deionized water to 50 ml. Ammonium hydroxide ( $\text{NH}_4\text{OH}$ , 30%, Carlo Erba) was pre-added to a digested  $\text{CaCO}_3$  solution to raise the pH level to 8–12 prior to the precipitation of HAP. 50 ml of a suspension containing  $\text{CaCO}_3$  was introduced into a 250 ml Erlenmeyer flask. The typical phosphorus sources,  $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$ , and  $(\text{NH}_4)_2\text{HPO}_4$ , were dissolved separately in 50 ml of deionized water at a molar ratio of Ca/P 1.7 and each solution was dripped into the alkaline  $\text{CaCO}_3$  solution, then stirred at  $50^\circ\text{C}$  under ambient pressure. The reaction was continued for 3 hours. The white solids collected by

filtration were oven dried at  $600^\circ\text{C}$  for 4 hours to yield a fine powder. The product was then rinsed with distilled water to dissolve any unreacted phosphate. The crystal phase of the synthesized powder was examined by an X-ray powder diffraction method using an X-ray diffractometer (Phillips Panalytical X'Pert Pro MPD). The diffraction patterns were collected over a  $2\theta$  range from  $10$  to  $80^\circ$  with a scan speed of  $0.5^\circ/\text{min}$ . A Fourier transform infrared (FT-IR, Shimadzu FTIR-8900) analysis using KBr method was also done. Microstructures of HAP obtained were examined by scanning electron microscopy (SEM, LEO 1450 VP).

## Results and Discussion

HAP was prepared by co-precipitation of non-digested  $\text{CaCO}_3$  and digested  $\text{CaCO}_3$  with various phosphorus sources ( $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$  and  $(\text{NH}_4)_2\text{HPO}_4$ ). The possible chemical reactions for the co-precipitation of non-digested  $\text{CaCO}_3$  may be expressed in Eq. (1)–(3) as:



The chemical reactions between digested  $\text{CaCO}_3$  with  $\text{CaCO}_3$  and formed  $\text{Ca}^{2+}$  ions and  $\text{CO}_2$ , reducing and phosphate can be expressed in Eq. (4)–(5).  $\text{CO}_3^{2-}$  substitution in HAP (Minh et al., 2012). The hydrogen ions from the acid solution reacted




The resulting products were examined by XRD. The resulting spectra may be seen in Figure 1. To compare the source of calcium between non-digested  $\text{CaCO}_3$  and the digested  $\text{CaCO}_3$  in the HAP

synthesis, the XRD results showed that HAP was synthesized by the non-digested  $\text{CaCO}_3$  with a reaction time of 18 hours. When Verwilghen et al. (2009) synthesized HAP starting from non-digested



$\text{CaCO}_3$  and monoammoniumphosphate at ambient pressure and  $60^\circ\text{C}$ , HAP was synthesized in 72 hours. The reaction of non-digested  $\text{CaCO}_3$  showed the XRD peak at about  $29.7^\circ$  indicating that carbonate was detected. As seen in Figure 1(a), the XRD pattern showed the existence of  $\text{CaCO}_3$ . For 18

hours period of reaction time, the process was gotten the better result. However, HAP was synthesized within 3 hours by the digested  $\text{CaCO}_3$  when reacted with various phosphorus sources ( $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$ , and  $(\text{NH}_4)_2\text{HPO}_4$ ) without any remaining  $\text{CO}_3^{2-}$ .

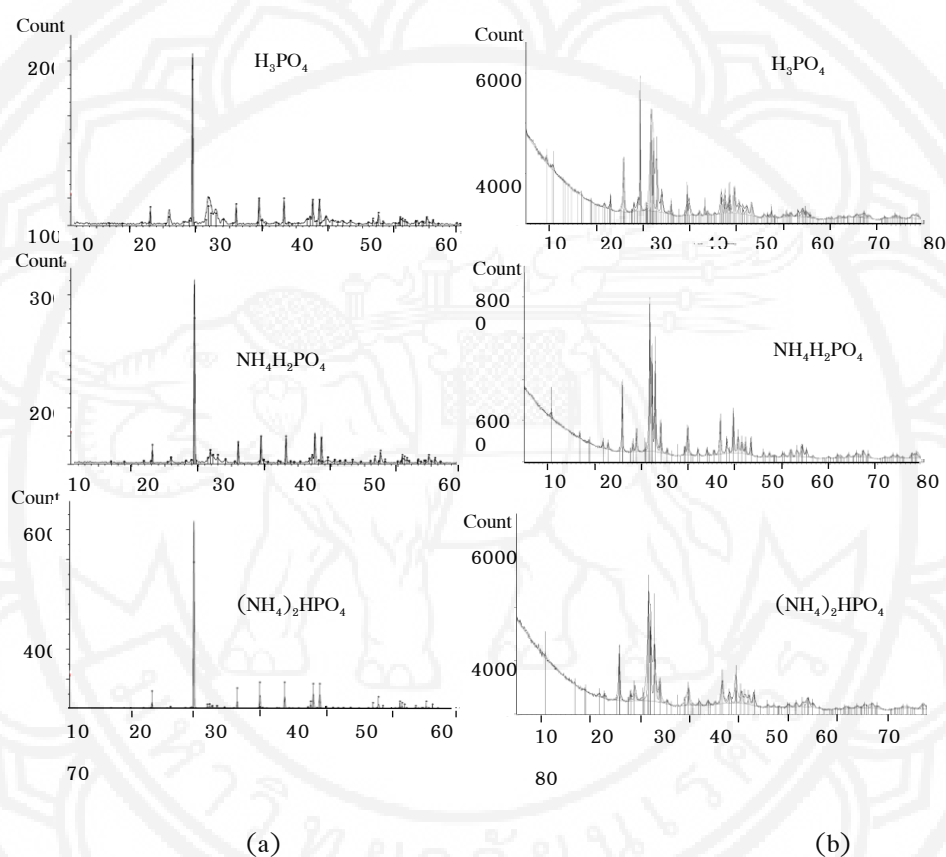


**Figure 1** XRD patterns of HAP syntheses using  $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$  and  $(\text{NH}_4)_2\text{HPO}_4$  as orthophosphate sources reacted with the non-digested  $\text{CaCO}_3$  at solution pH 9 for (a) 3 h and (b) 18 h.

As seen in Figure 1, the identification of HAP was primarily based on the two most prominent peaks at  $26^\circ$  and at  $32-34^\circ$ . The presence of HAP's characteristic diffraction peaks near  $25^\circ$ ,  $33^\circ$ ,  $40^\circ$ , and  $50^\circ$  confirmed that the synthesized material was HAP (Piantone et al., 2003). All XRD patterns matched with HAP reference data and showed little change in  $2\theta$  and sharpness of the peaks for the various phosphorus sources ( $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$ ,

and  $(\text{NH}_4)_2\text{HPO}_4$ ). From the results, the appropriate time of reaction for non-digested  $\text{CaCO}_3$  was 18 hours. Therefore, the digestion of  $\text{CaCO}_3$  reduced the preparation time of HAP and decreased the presence of  $\text{CO}_3^{2-}$  in HAP. Minh et al. (2012) described a reaction pathway of the co-precipitation of HAP in acidic conditions in Figure 2. First,  $\text{CaCO}_3$  powder was digested in acid solution to form soluble calcium cations. These cations were then

precipitated with orthophosphate anions to form mono-calcium phosphate monohydrate ( $\text{Ca}(\text{H}_2\text{PO}_4)_2 \cdot \text{H}_2\text{O}$ ) and dicalcium phosphate dihydrate ( $\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$ ) or brushite as the first intermediates.  $\text{Ca}(\text{H}_2\text{PO}_4)_2 \cdot \text{H}_2\text{O}$  evolved to  $\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$  by the reaction with more calcium cations.  $\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$  was then transformed into


dicalcium phosphate anhydrous ( $\text{CaHPO}_4$ ) as another intermediate and finally  $\text{Ca}_5(\text{PO}_4)_3\text{OH}$ . In acidic condition, the presence of carbonic gas or (bi) carbonate anions in the reaction mixture led to the formation of B-type calcium carbonate-apatite (CAP) in parallel with the formation of calcium hydroxyapatite as the final product.

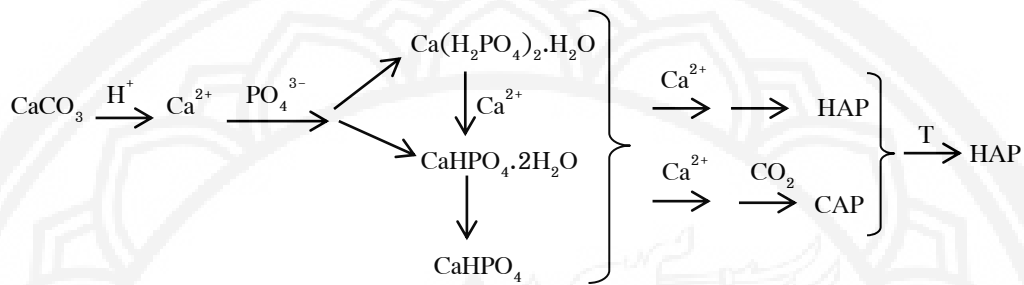


**Figure 2** Reaction pathway in the HAP synthesis (Minh et al., 2012).

The FT-IR spectra of synthesized HAP by  $\text{CaCO}_3$  digestion are shown in Figure 3-5. The spectra indicated absorption bands at 563, 604 and 1032  $\text{cm}^{-1}$ , corresponding to  $\text{PO}_4^{3-}$  ions, and a broad band at around 3500  $\text{cm}^{-1}$  and 640  $\text{cm}^{-1}$ , corresponding to a  $\text{PO}_4^{3-}$  group which confirmed the formation of the characteristic HAP structure containing a hydroxyl group. The apatite lattice can be substituted by  $\text{CO}_3^{2-}$  ions, known respectively as A-type and B-


type substitutes. The FTIR spectrum showed without the characteristic bands of B-type  $\text{CO}_3^{2-}$  substitution at 874  $\text{cm}^{-1}$  (v2) and 1421-1473  $\text{cm}^{-1}$  (v3). Furthermore, there was no characteristic peak of A-type  $\text{CO}_3^{2-}$  substitution at 1540  $\text{cm}^{-1}$ . The results showed that the preparation of HAP from  $\text{CaCO}_3$  digestion decreased the  $\text{CO}_3^{2-}$  substitution in HAP (Hui, Meena, Singh, Agarawal, & Prakash, 2010).

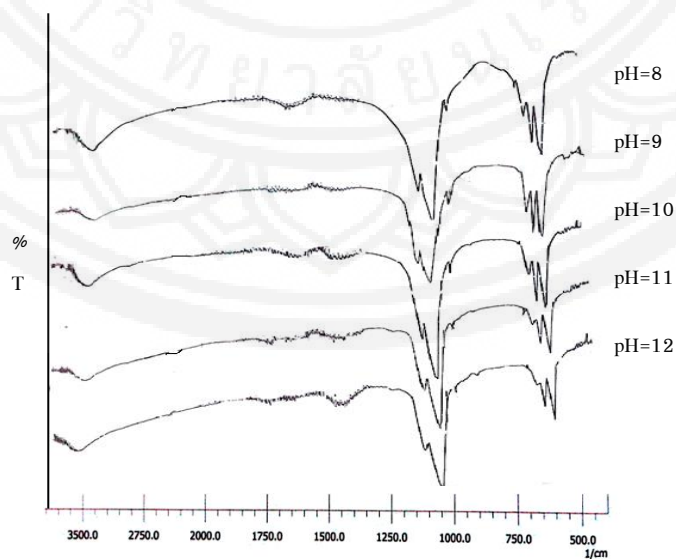


**Figure 3** Infrared spectra of HAP prepared by co-precipitation of  $\text{H}_3\text{PO}_4$  with digested  $\text{CaCO}_3$ .

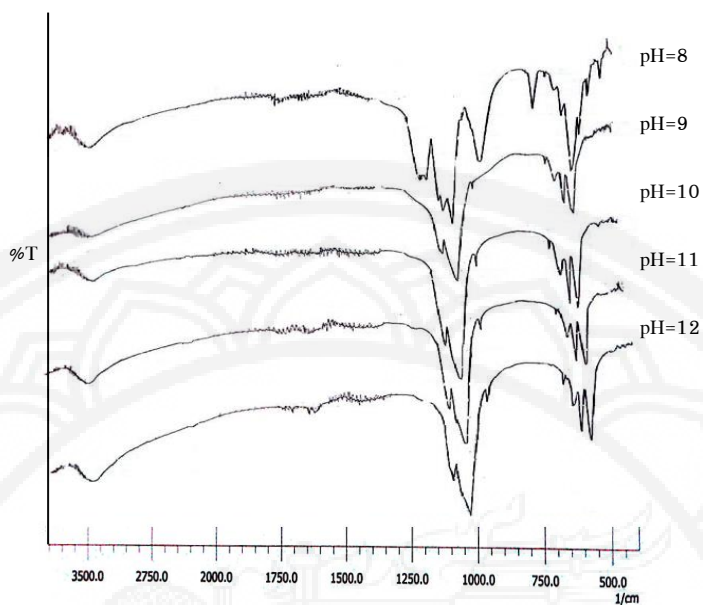

**Figure 4** Infrared spectra of HAP prepared by co-precipitation of  $\text{NH}_4\text{H}_2\text{PO}_4$  with digested  $\text{CaCO}_3$ .

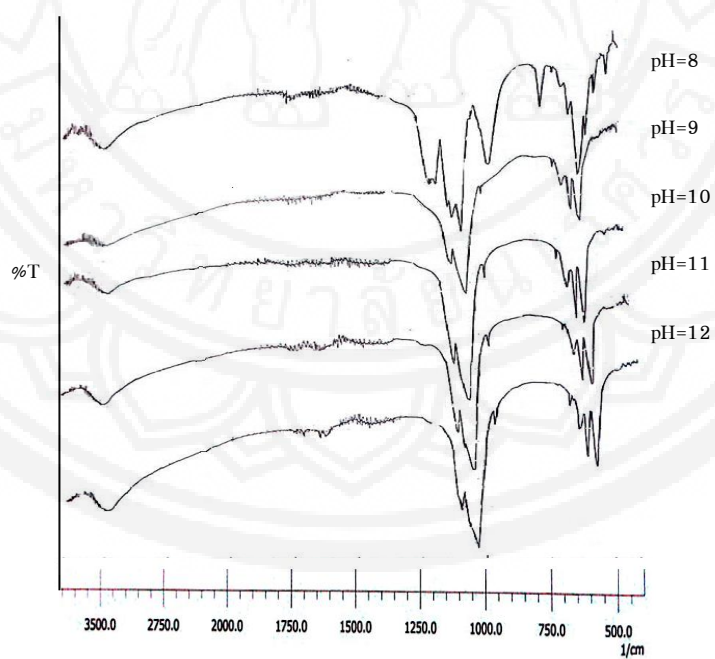

**Figure 5** Infrared spectra of HAP prepared by co-precipitation of  $(\text{NH}_4)_2\text{HPO}_4$  with digested  $\text{CaCO}_3$ .

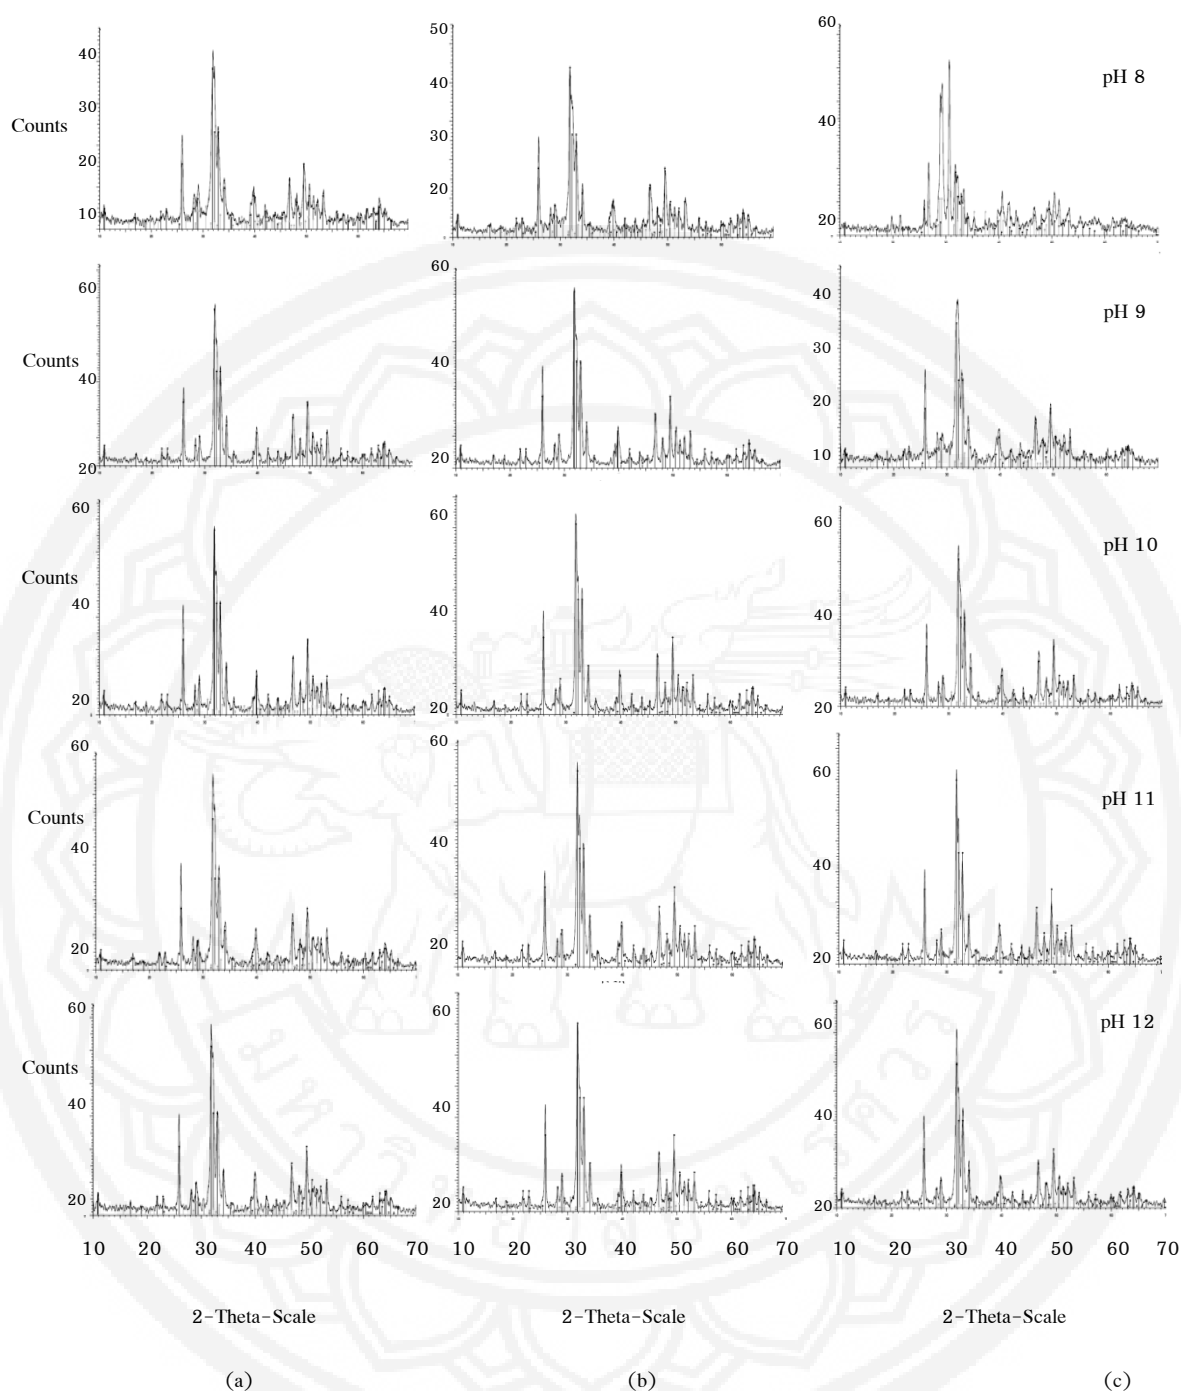

**Figure 6** XRD patterns of HAP in the syntheses using  $H_3PO_4$  (a),  $NH_4H_2PO_4$  (b) and  $(NH_4)_2HPO_4$  (c) as orthophosphate sources reacted with the digested  $CaCO_3$  at pH 8–12 for 3 h.


The precipitation of HAP from digested  $CaCO_3$  was observed at pH 8–12. The FTIR spectra (Figure 3–5) of all samples have shown bands corresponding to HAP structure. Similarly, the results from XRD patterns (Figure 6) have shown that the samples

underwent a pure apatite phase and the sharp peaks confirm that they were well crystallized. It indicated that the different selections of pH value (pH 8–12) were successful to prepare HAP by digested  $CaCO_3$ . According to the study of the precipitation of calcium



phosphates as a function of the concentration of the calcium ions, phosphate ions and the pH at constant ionic force by Recillas et al. (2012) found that at pH = 6 there is no precipitation, and at a pH higher than 7.4 it is feasible that HAP and TCP will precipitate. One must recall the following facts:  $\text{CaCO}_3$  was unstable under acidic pH conditions, but reaction with phosphoric acid produces poorly soluble monetite coatings which block further reaction.

Furthermore, HAP was formed at basic pH levels, where  $\text{CaCO}_3$  was stable and no reaction was expected unless the system was heated under pressure such as takes place in the hydrothermal process. At ambient pressure, hydrogenphosphate groups were first absorbed on the carbonate surface, and then were deprotonated to form calcium orthophosphate, releasing the carbonate ions into the solution (Verwilghen et al., 2009).

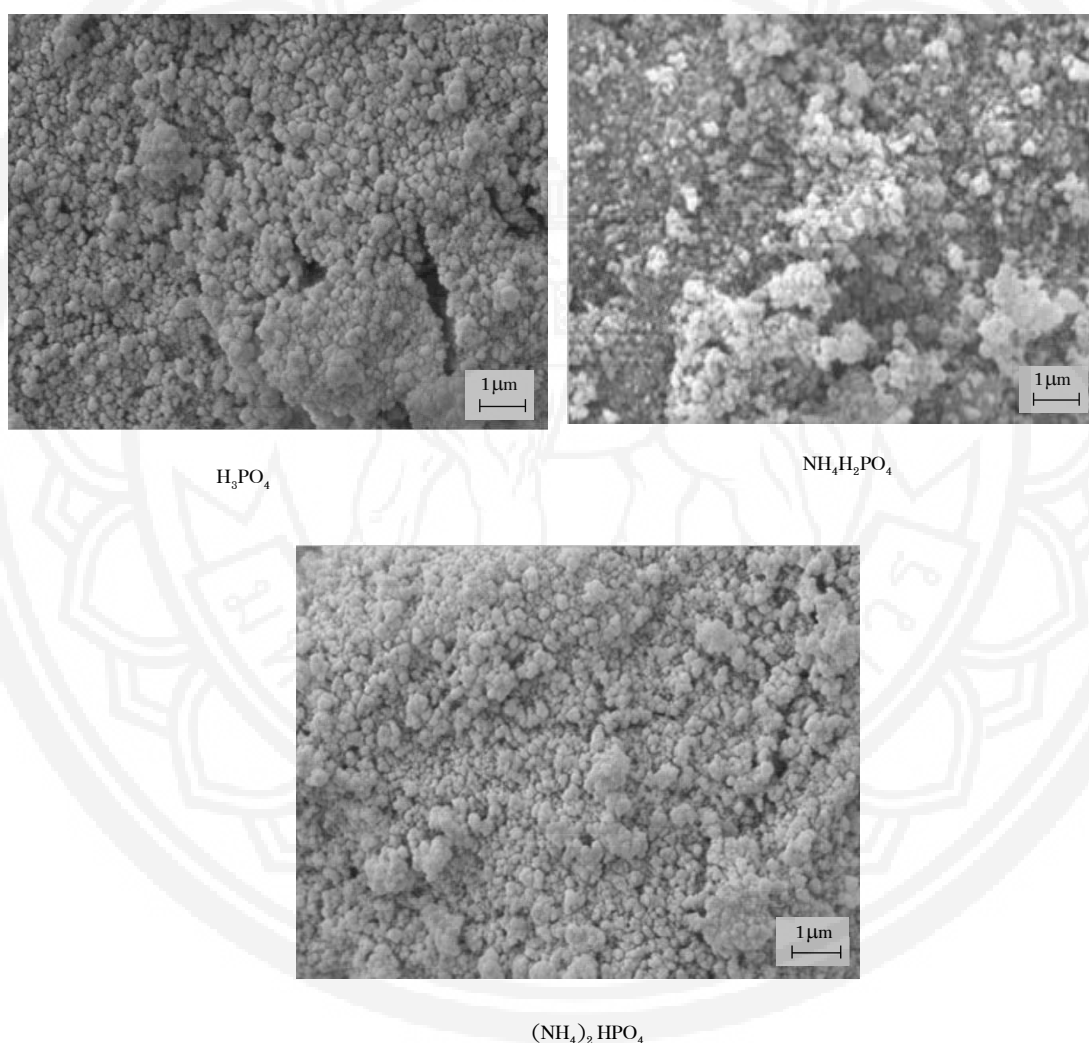

**Figure 7** SEM analysis of synthetic HAP using  $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$  and  $(\text{NH}_4)_2\text{HPO}_4$  as orthophosphate sources reacted with the digested  $\text{CaCO}_3$  at pH 9 for 3 h.

The synthetic HAP using  $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$  and  $(\text{NH}_4)_2\text{HPO}_4$  as orthophosphate sources reacted with the digested  $\text{CaCO}_3$  at pH 9 obtained after

3 hours of reaction was analyzed by SEM. Figure 7 depicted a SEM micrograph of HAP powder, that's morphology was characterized by agglomerated





nanoparticles with sizes smaller than 1  $\mu\text{m}$ . The shapes of which were almost the same and the size was always between 0.5  $\mu\text{m}$  and 2  $\mu\text{m}$ , built up from fine particles about 100–300 nm in size. Individual fine particles with spherical and semi-spherical shapes were observed. The agglomerates were irregular ovular shapes and spherical shapes.

### Conclusion

In this study,  $\text{CaCO}_3$  was digested before co-precipitation with the various phosphorus sources ( $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$ , and  $(\text{NH}_4)_2\text{HPO}_4$ ). This new synthetic pathway produced HAP without the creation of  $\text{CO}_3^{2-}$ . The  $\text{Ca}^{2+}$  ions released by the digestion of  $\text{CaCO}_3$  were then used as reactants in the formation of HAP. It is noteworthy that  $\text{Ca}^{2+}$  ions barely appear in the HAP structure. The conclusion of the experiment with prevented the presence of  $\text{CO}_3^{2-}$  in HAP. The effect of the reagents, such as  $\text{H}_3\text{PO}_4$ ,  $\text{NH}_4\text{H}_2\text{PO}_4$ , and  $(\text{NH}_4)_2\text{HPO}_4$ , indicated that all of the phosphates could be used successfully in the production of HAP. The results of testing various pH levels indicate that a pH of 8–12 is required in the successful production of HAP using the digested  $\text{CaCO}_3$ .

### Acknowledgement

The authors wish to thank Thepsatri Rajabhat for provision of the laboratory facilities which enabled this work to be carried out and also Bureau of the Budget for financial support.

### References

- An, G. H., Wang, H. J., Kimb, B. H., Jeong, Y. G., & Choa, Y. H. (2007). Fabrication and characterization of a hydroxyapatite nanopowder by ultrasonic spray pyrolysis with salt-assisted decomposition. *Materials Science and Engineering A*, 449–451, 821–824. Retrieved from <http://dx.doi.org/10.1016/j.msea.2006.02.436>
- Bezzi, G., Celotti, G., Landi, E., La Torretta, T. M. G., Sopyan, I., & Tampieri, A. (2003). A novel sol-gel technique for hydroxyapatite preparation. *Materials Chemistry and Physics*, 78, 816–824.
- Bouyer, E., Gitzhofer, F., & Boulos, M. I. (2000). Morphological study of hydroxyapatite nanocrystal suspension. *Journal of Material Science: Materials in Medicine*, 11, 523–531.
- Hui, P., Meena, S. L., Singh, G., Agarawal, R. D., & Prakash, S. (2010). Synthesis of Hydroxyapatite Bio-Ceramic Powder by Hydrothermal Method. *Journal of Minerals & Materials Characterization & Engineering*, 9, 683–692.
- Inthong, S., Tunkasiri, T., Eitssayeam, S., Pengpat, K., & Rujjanagul, G. (2013). Physical properties and bioactivity of nanocrystalline hydroxyapatite synthesized by a co-precipitation route. *Ceramics International*, 39, S533–S536. Retrieved from <http://dx.doi.org/10.1016/j.ceramint.2012.10.129>
- Kim, Y., & Ohtsuki, C. (2016). Hydroxyapatite formation from calcium carbonate single crystal under hydrothermal condition: Effects of processing temperature. *Ceramics International*, 42, 1886–



1890. Retrieved from <http://dx.doi.org/10.1016/j.ceramint.2015.09.156>
- Kong, L. B., Ma, J., & Boey, F. (2002). Nanosized hydroxyapatite powders derived from coprecipitation process. *Journal of Materials Science*, 37, 1131–1134.
- Mahabole, M. P., Aiyer, R. C., Ramakrishna, C. V., Sreedhar, B., & Khairnar, R. S. (2005). Synthesis, characterization and gas sensing property of hydroxyapatite ceramic. *Bulletin of Materials Science*, 28(6), 535–545.
- Minh, D. P., Lyczko, N., Sebei, H., Nzihou, A., & Sharrock, P. (2012). Synthesis of calcium hydroxyapatite from calcium carbonate and different orthophosphate sources: A comparative study. *Materials Science and Engineering B*, 177, 1080–1089. Retrieved from <http://dx.doi.org/10.1016/j.mseb.2012.05.007>
- Nasiri-Tabrizi, B., Honarmandi, P., Ebrahimi-Kahrizsangi, R., & Honarmandi, P. (2009). Synthesis of nanosize single-crystal hydroxyapatite via mechanochemical method. *Materials Letters*, 63, 543–546. Retrieved from <http://dx.doi.org/10.1016/j.matlet.2008.11.030>
- Piantone, P., Bodéan, F., Derie, R., & Depelsenaire, G. (2003). Monitoring the stabilization of municipal solid waste incineration fly ash by phosphation: mineralogical and balance approach. *Waste Management*, 23, 225–243.
- Recillas, S., Rodríguez-Lugo, V., Montero, M. L., Viquez-Cano, S., Hernandez, L., & Castaño, V. M. (2012). Studies on the precipitation behavior of calcium phosphate solutions. *Journal of Ceramic Processing Research*, 13(1), 5–10.
- Sonoda, K., Furuzono, T., Walsh, D., Sato, K., & Tanaka, J. (2002). Influence of emulsion on crystal growth of hydroxyapatite. *Solid State Ionics*, 151, 321 – 327.
- Verwilghen, C., Chkir, M., Rio, S., Nzihou, A., Sharrock, P., & Depelsenaire, G. (2009). Convenient of Calcium Carbonate to Hydroxyapatite at Ambient Pressure. *Material Science and Engineering C*, 29, 771–773. Retrieved from <http://dx.doi.org/10.1016/j.msec.2008.07.007>
- Waheeda, S., Sultana, M., Jamila, T., & Hussain, T. (2013). Comparative analysis of hydroxyapatite synthesized by sol-gel, ultrasonication and microwave assisted technique. *Proceedings of the International Conference on Solid State Physics 2013 (ICSSP'13)*, 2(2015), 5477–5484. Retrieved from <http://dx.doi.org/10.1016/j.matpr.2015.11.073>